


### 石英透過率波長特性 (T=10mm)



波長nm	石英屈折率	波長nm	石英屈折率
184.9	1.57518	632.8	1.45714
193.4	1.56036	656.3	1.45649
206.2	1.54281	706.5	1.45526
214.4	1.53386	780.0	1.45379
228.8	1.52129	852.1	1.45259
248.3	1.50852	1014.0	1.45036
253.7	1.50565	1128.6	1.44899
289.4	1.49112	1529.6	1.44440
334.1	1.47989	1813.1	1.44084
365.0	1.47466	1970.1	1.43867
404.7	1.46974	2058.1	1.43737
435.8	1.46681	2325.4	1.43309
486.1	1.46324	vd	67.9±0.2
587.6	1.45858	info@akatsuki-tech.com 暁明技術株式会社	

### 石英屈折率と波長の関係

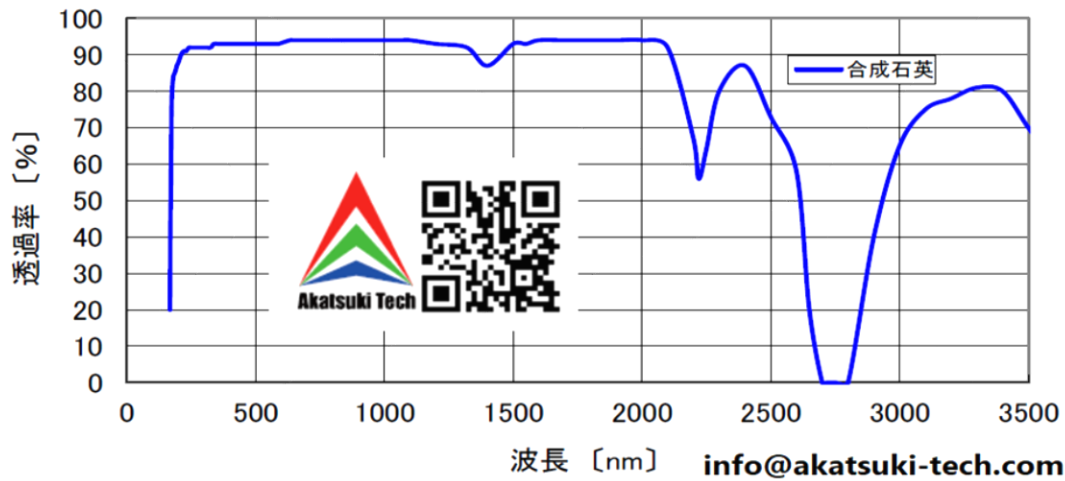